



Original Article

Decolorization of Textile Wastewater Using Fabricated Poly Acrylonitrile (PAN) Nanoparticles

Omnya A. El-Batrawy^{1*}, Mahmoud S. Ibrahim¹, Hala Fakhry^{1,2} and M. R. El-Aassar²

¹Environmental Sciences Department, Faculty of Science, Damietta University, New Damietta City, Damietta, 34517, Egypt.

²Polymer Materials Research Department, Advanced Technology and New Materials Researches Institute, City of Scientific Researches and Technological Applications, New Borg El-Arab City, Alexandria, 21934 Egypt.

Article Info

Article history:

Received 22/4/2018

Received in revised form 11/6/2018

Accepted 14/6/2018

Keywords:

Dye removal

Basic Red 46

Batch Mode Experiments

Adsorption isotherm

Kinetic Models

Abstract

Water contamination is not only influence human health and environment, but it has also effects on social and economic costs. Textile wastewater is considered to be one of the most dangerous types of water contaminants as it consists of mixture of pigments, dyes and different types of organic contaminants. Nanotechnology offers novel functional materials in the area of wastewater treatment especially dye removal. Polyacrylonitrile (PAN) nanoparticles considered to be one of the most promising prepared materials in the field of dye removal. PAN nanoparticles was prepared by precipitation polymerization technique in an alcoholic aqueous solution (water: ethanol) and was characterized using scanning electron microscope (SEM), Fourier Transfer infrared spectrophotometer (FT-IR) and Thermal Gravimetric Analysis (TGA). Basic Red 46 (BR 46) dye is a cationic dye which is used as a model of contaminant due to its extensive use in textile industry. The processing parameters affecting on the adsorption of BR 46 onto the prepared PAN nanoparticles have been optimized through a batch mode experiments. The maximum removal percentage of the selected dye was 62.4 % recorded after 240 min equilibrium time using 0.05 g from PAN nanoparticles and with 5 ppm initial dye concentration. As the experimental results proved that the increment in material dosage from 0.01 to 0.5 g enhanced the dye removal percentage from 43.6% up to 85%. Meanwhile, the improvement in initial dye concentrations had negative impact on the adsorption process onto the prepared powdered material, as it decreased from 82.3 to 11.85% when the initial dye concentration increased from 1-100 ppm. The dye adsorption mechanism was investigated through the application of Langmuir and Freundlich isotherm models on the experimental data. Moreover, the kinetics of dye adsorption process was tested using the pseudo-first and pseudo-second order kinetic models.

1. Introduction

Rapid industrialization has resulted in the generation of large amounts of wastewater that affect adversely on environment. Textile wastewater is a mixture of colorants (dyes and pigments) and various organic compounds used as cleaning solvents, plasticizers etc. (Crini and Badot, 2008). Textile wastewater contains colored organic compounds as their color renders them esthetically unacceptable. Color is the first contaminant to be recognized in wastewater and cause serious ecological problems (Sharma *et al.*, 2007).

Organic dyes are considered to be one of the most serious and dangerous water contaminants, as they intensively used in a lot of industries as leather goods, paper, cosmetics, textile

etc. These dyes which released with the waste effluents undergo chemical changes, decrease dissolved oxygen, increase chemical oxygen demand (COD) and destroy aquatic ecology. Moreover, they cause carcinogenic and genotoxic effects on human life (Prachi *et al.*, 2013). Therefore, the decolorization of toxic organic dyes from wastewater before discharging them into natural water streams has received a great deal of attention recently (Aksakala and Uzun, 2010; El Haddad *et al.*, 2012; Haider *et al.*, 2014; Hu *et al.*, 2017). In recent years, numerous methods as flocculation, adsorption, photo degradation and chemical oxidation have been developed to treat wastewater containing dye stuffs (Ibrahim *et al.*, 2017). Among them, adsorption technique has been recognized as a promising technique due to its high efficiency, simplicity of design, ease of operation as well as the wide suitability for diverse types of dyes (Han *et al.*, 2017).

*Correspondence author:

E-mail address: om_elbatrawy@du.edu.eg; om_elbatrawy@hotmail.com

Tel.: 01003479359

Nanotechnology offers novel functional materials, processes and devices with unique activity toward wastewater treatment. Many nano-based environmental technologies are expected to improve or replace various conventional environmental technologies in the near future (Sun *et al.*, 2006, Satapanajaru *et al.*, 2011 and Prachi *et al.*, 2013). Generally, nano-polymeric adsorbents have unique adsorptive properties and capacities for dye removal (Prachi *et al.*, 2013). Poly acrylonitrile (PAN) are considered to be an outstanding material for environmental applications due to its good mechanical properties, moderate separating properties, unique thermal properties and good solvent resistance (Mahmoodi *et al.*, 2011 and Hadi, 2013). It is also an excellent material in the purification of dyes and heavy metals from wastewater (Musale and Kumar, 2000).

Basic Red 46 (BR 46) dye was used as a contaminant in a synthetic wastewater model as it is used intensively in textile industry; also its release into the environment is of concern due to their toxic, mutagenic and carcinogenic characteristics (Kaouah *et al.*, 2013). The present study is focused on the preparation of PAN nanoparticles through precipitation polymerization technique with the ability to remove BR 46 from aqueous solution. Moreover, the influence of different processing parameters affecting on dye adsorption process onto the prepared PAN nanoparticles will be monitored.

2. Material and Methods

2.1. Materials

Potassium persulfate (K₂S₂O₈) and acrylonitrile (AN) were obtained from BDH (London, UK). The selected dye; azo dye of Basic Red 46 (BR 46); was obtained from Amria textile factory (Alexandria, Egypt). All other chemicals were of analytical grade and were purchased from Sigma.

2.2. Preparation of PAN Nanoparticles

PAN powdered nanoparticles was prepared using simple precipitation polymerization technique in the presence of K₂S₂O₈ as an initiator (El-Aassar, 2013). The polymerization process was done through the dissolution of AN monomers in 0.01 M K₂S₂O₈ alcoholic solution of water: ethanol (1:1) as cosolvent at the room temperature. The total volume of monomer to the cosolvent is 10%. For completeness of the polymerization process the previous polymerization solution was stirred in a thermostatic water bath for 4 h at 55°C. The obtained powder washed by ethanol–water solution repeatedly to dispose of un-reacted monomer and initiator. The gained powder was dried in oven over night at 45°C then grinded to the desired mesh size.

2.3. Preparation of Adsorbate Solution

Basic Red 46 (BR 46) dye is a cationic dye and its molecular structure was illustrated in Figure 1 (Sarioglu *et al.*, 2007). The used stock dye solution was 100 ppm.

2.4. Characterization of Prepared PAN Nanoparticles

2.4.1 Scanning Electron Microscopic Analysis (SEM)

The scanning electron microscope (JEOL JSM 6360LA, Japan) images of the prepared PAN nanoparticles were obtained by putting the materials onto carbon tape-attached aluminum SEM holders then; the particles were coated with gold to a few nanometer thicknesses under vacuum.

2.4.2 Fourier Transform Infrared Spectroscopic Analysis (FT-IR)

An FT-IR spectrum (Jasco-4100) of the prepared PAN nanoparticles was carried out with a FT-IR spectrometer in the spectral range of 4,000–500 cm⁻¹.

2.4.3 Thermo Gravimetric Analysis (TGA)

A thermo gravimetric analyzer (TGA-50 Shimadzu) was used to carry out the thermal analysis of the prepared PAN nanoparticles. About 6 mg of particles were put in ceramic pans of TGA instrument and the thermal analysis was carried out over the temperature range of 0–600°C with 10°C/min heating rate under dry N₂ flow and 10 mL/min rate.

2.5. Batch BR 46 Adsorption Experiments

A batch process technique was used to evaluate the adsorption behaviour of the prepared PAN nanoparticles through a series of batch adsorption experiments were performed in order to evaluate the prepared PAN nanoparticles as dye removing agent from aqueous solutions. Studies were carried out in triplicate to get concordant results using a batch adsorption technique.

Different processing parameters affecting on the adsorption process of BR 46 onto the prepared PAN nanoparticles such as contact time, initial dye concentration, solution pH, adsorbent dosage and solution temperature had been optimized. The adsorption process mechanism had been studied through the addition of 0.05g of the prepared PAN nanoparticles to 20 ml of 10 ppm of BR 46 dye solution. The mixture was shaken at 400 rpm for a predetermined period of time, then, withdrawn the clear supernatant and centrifuged for 15 min at 15,000 rpm. The absorbance of the remaining solutions is measured at a maximum wavelength of 530 nm using a double beam UV/vis spectrophotometer (Jenway 6305). Figure 2 represents an illustration scheme of dye removal process using PAN Nanoparticles.

The amount of dye adsorption at equilibrium (mg/g) was calculated from the following equation:

$$qe = \frac{(C_0 - C_e)v}{w} \quad (1)$$

where C₀ is the initial dye concentration, C_e (mg/L) is the concentration of the used dye at equilibrium, V (L) is the solution volume and W (g) is the adsorbent mass.

The removal percentage of the used dye was calculated by the following equation:

$$\% \text{ of dye removal} = \frac{C_0 - C_e}{C_0} * 100 \quad (2)$$

where C_0 and C_e (mg/L) are the concentrations of dye at the initial and equilibrium stages.

2.6. Kinetic and Equilibrium Behaviors of BR 46 Dye Adsorption Process onto the Prepared PAN Nanoparticles.

The adsorption process of Basic Red (BR 46) dye onto the prepared PAN particles were investigated using Langmuir and Freundlich equilibrium isotherm models. Moreover, the kinetics of dye adsorption process was tested using the pseudo-first and pseudo-second order kinetic models.

3. Results and Discussion

3.1. Characterization of PAN Powder Nanoparticles

3.1.1. Morphological Characterization [Scanning Electron Microscopy (SEM)]

The morphological structure of the prepared PAN nanoparticles was investigated using scanning electron microscope image (Figure 3). It was so obvious from figure 3 that the prepared PAN nanoparticles doesn't have any definite structure, has irregular form with a high degree of heterogeneity; also, from the first look to the figure, it looks like a huge bulk of particles within the micro scale.

3.1.2. Fourier Transform Infrared Spectroscopic Analysis (FT-IR) Spectra

FT-IR spectra technique was used to identify the main functional groups that located on the prepared material and responsible for dye adsorption process. Figure 4 showed a broad band at 3471.98/cm for (O-H) water bond. Also, the representative band at 2249.07/cm is attributed to $C\equiv N$ bonding. The characteristic band at 1444.73/cm represents $C=C$; however, the identified band 2249.07/cm is assigned for C-H. These results confirmed the formation of PAN polymeric material through the presence of its characteristic peaks.

3.1.3. Thermo Gravimetric Analysis (TGA) Analysis

Thermo Gravimetric Analysis (TGA) is a thermal analysis method in which any increasing in material temperature (with constant heating rate) leads to changes in its physical and chemical properties or as a function of time (with constant temperature and/or constant mass loss) (Coats and Redfern, 1963). The main degradation step of PAN nanoparticles began at 27.7°C and ended at 295.40°C with a percentage of weight losses of 1.172 % which represented the physical water adsorbed onto PAN; this was showed through the first pattern of PAN (Figure 5). The second step of degradation began at 295.40°C and ended at 405.93°C with percentage of weight losses of 7.855%. The last degradation step began at 405.93°C and end at 472.30°C with percentage of weight losses of 6.654%.

3.2. Decolorization of BR (46) using the Prepared PAN Nanoparticles

3.2.1. Effect of BR (46) Initial Concentration

The removal percentage of dye depends on the initial dye concentration. It was observed from Figure (6) that the Basic Red 46 removal percentage is inversely proportional to the initial dye solution concentration as it decreased from 82.3 to 11.8% when the dye concentration increased from 1-100 ppm using PAN nanoparticles. This behaviour might be attributed to the repulsive forces between the dye molecules on the prepared PAN nanoparticles surface and the bulk phase (Crini and Badot, 2008; Salama, 2017). At lower dye concentrations, the ratio between the numbers of dye molecules to the available active sites located on the adsorbent surface is low. However, at high concentration the available sites of adsorption become fewer, and hence the percentage removal of dye depends upon concentration of nanopolymeric nanoparticles (El Haddad *et al.*, 2012). Also, the reduction in dye removal might be due to saturation of adsorption active sites on the material surface as the concentration of dye increases (Tiwari *et al.*, 2014).

3.2.2. Effect of the Contact Time

The effect of contact time on the adsorption of basic red dye onto the prepared PAN nanoparticles was investigated over 270 min time intervals (Figure 7). The removal of the used dye was increased with increasing contact time between dye and the prepared material at initial dye concentration of 5mg/L. The removal percentage of dye using PAN nanoparticles increases from 9.2 % up to 62.4 % when the contact time between dye and PAN nanoparticles increase from 5 to 240 minutes. Relatively fast equilibrium has been achieved due to the large amount of available active sites at the surface of the prepared PAN nanoparticles. After the equilibrium time (240 min) slightly increase in the removal percentage had been noticed as the surface of the prepared material almost might be occupied with the dye molecules. It was found that, a large number of unoccupied surface active sites are obtainable for adsorption during the first stage, and continuous occupation of these sites decreased the rate of reaction and subsequently reduce adsorption efficacy (Araujo and Teixeira, 1997, Srivastava *et al.*, 2006; Srivastava *et al.*, 2008 and Kalavathy and Miranda, 2010). This behavior might also be due to the aggregation of dye molecules around PAN particles which might block the migration of dye molecules as the PAN active sites become saturated and improve resistance of diffusion of dye molecules into the adsorbents (EL-kady *et al.*, 2018). Similar trend was obtained in the adsorption of MB on sulfonic acid group modified MIL-101 (Luo *et al.*, 2016).

3.2.3. Effect of PAN Adsorbent Dosage

The effect of the prepared PAN nanoparticles dosage on the percentage of dye removal was studied after 240 min (Figure 8), different weights of PAN nanoparticles (0.01, 0.05,

0.1, 0.2, 0.3, 0.4 and 0.5 g.) was used at equilibrium. The BR 46 percentage removal was increased with increasing adsorbent doses due to the occurrence of more active sites on the PAN surface which increase the active functional groups at higher adsorbent dosages. The maximum dye removal percentage of 88.6% was recorded using 0.5g of PAN nanoparticles. Moreover, the decrease of sorption capacity with raising material dose might be due to the presence of more active sites on the material surface as adsorption capacity increase in the first stage of adsorption, but further increase in material dose saturates the adsorbents and there was a steady state (Tiwari *et al.*, 2014). It is as a result of dye molecules aggregation on the adsorption sites that decrease the adsorption efficiency. Also, there will be overlapping of adsorption sites because of overcrowding of material particles (Gorza *et al.*, 2017). The same behaviour was also illustrated by Deniz and Karaman (2011) as they found that, the removal percentage of BR 46 increased with the increase of material dose.

3.2.4. Effect of Solution pH on Dye Adsorption

The dye solution pH plays an important role in the adsorption process in the field of dye wastewater treatment (Lou *et al.*, 2018). It was indicated that the pH significantly affected the extent of adsorption of dye and the removal of BR 46. The removal percentage of BR 46 onto prepared PAN nanoparticles increased from 40.7 % to 96.3 % when the solution pH rose from 1 to 13 (Figure 9). This behavior might be attributed to the cationic nature of the used dye which has naturalization trend in alkaline media better than acidic medium (Janaki *et al.*, 2012). In basic solution the electrostatic interaction between the dye cation and PAN was increased as the materials surfaces were negatively charged due to the presence of excess OH⁻ (EL Alouani *et al.*, 2018), however in acidic solution the presence of H⁺ may compete with the dye cations, which results in lower adsorption of dye on the prepared material chain (Hameed and Ahmad 2009). This is agreed well with (Karim *et al.*, 2009), as they mention that, the adsorption capacity of BR46 onto the prepared clay significantly increased when the dye solution pH increased from 9.5 to 12. In basic conditions, the clay surface which has a negative charge favours the BR46 adsorption and subsequently, the amount of BR46 adsorbed onto the prepared clay decreased with the decrease of pH.

3.2.5. Effect of Temperature on Dye Adsorption:

The effect (influence) of temperature on the adsorption rate of BR46 on PAN nanoparticles was investigated at 25, 35, 45 and 75°C. The percentage of dye removal increased from 50.1 to 85 % when temperature of the solution was increased from 25 to 75°C, indicating that the process is an endothermic (Figure 10). Raising temperature is expected to increase the diffusion rate of dye particles through the outer layer and in the internal pores of the material particle, as the solution viscosity decreased (Wua *et al.*, 2011). Moreover, the

equilibrium capacity of the prepared materials will be changed by changing temperature (Al-Qodah, 2000). Also, with increasing temperature the motion of dye molecules increased (Alkan and Dogan, 2003).

3.3. Adsorption Equilibrium

When the adsorption process reached the equilibrium, the process which described the distribution of molecules between liquid and solid phase called adsorption isotherms or adsorption equilibrium (Abu-Saied *et al.*, 2013). Adsorption isotherm is used to explain how adsorbates interact with adsorbents and to optimize the adsorbents dosage. Therefore, finding out a suitable model of isotherms data was a must and this was done by fitting them to different isotherm models (Jianlong *et al.*, 2001). The effect of material dosage concentration was monitored in a batch mode experiments at the adsorption equilibrium time of 240 min in order to study the equilibrium sorption of BR 46 dye onto the prepared PAN nanoparticles. The isotherm data gained from this study were fitted to the Langmuir and Freundlich isotherms.

The adsorption equilibrium of BR 46 onto the prepared PAN nanoparticles as adsorbent material was investigated by Langmuir equation. Langmuir isotherm model assumes monolayer coverage and uniform activity distribution on the adsorbent surface. Figure 11 indicates a straight line with high correlation coefficient value (R²= 0.98) for the linearized plot of the equation that is expressed as:

$$\frac{C_e}{q_e} = \frac{1}{q_m K} + \frac{C_e}{q_m} \quad (3)$$

Where q_e is the amount of adsorbed dye (mg/g), C_e is the equilibrium concentration of the adsorbate ions (mg/L), and q_m and K are Langmuir constants related to maximum adsorption capacity (monolayer capacity) (mg/g) and energy of adsorption (L/mg), respectively. Therefore, the Langmuir isotherm model can describe Basic Red 46 dye sorption onto PAN nanoparticles. As Langmuir isotherm model supposes a monolayer coverage and uniform activity distribution on the adsorbent surface, it was more appropriate to explain the experimental data compared with Freundlich isotherm model. Langmuir parameters for Basic Red 46 dye removal (q_m and K), were calculated and tabulated at Table 1. The calculated value of monolayer adsorption capacity q_m is equal to 200 mg of BR 46 dye/g of the PAN nanoparticles. It was concluded that the prepared PAN material is appropriate for Basic Red 46 dye removal with energy of sorption equal to 0.189 mg/L.

The Freundlich isotherm doesn't describe the monolayer sorption capacity in contrast to the Langmuir model (Mohy Eldin *et al.*, 2010). Freundlich isotherm model supposedly heterogeneous site energies and no limited levels of sorption. It has been shown to be reliable with the exponential distribution of active centers, which is characteristic of heterogeneous surfaces (Bayramoglu and Arica, 2013).

The linearized form of the *Freundlich* equation may be expressed as:

$$\ln q_e = \ln K_F + \frac{1}{n_f} \ln C_e \quad (4)$$

where q_e is the amount of dye adsorbed at equilibrium (mg/g); C_e is the equilibrium concentration of the adsorbate (mg/L); and K_F and n_f are Freundlich constants related to the adsorption capacity and adsorption intensity, respectively. Figure 12 indicates a straight line with low value of the correlation coefficient ($R^2 = 0.95$) for the linearized plot of the equation compared with the Langmuir correlation coefficient. Roughly, the intercept of the line, K_F , indicates adsorption capacity, and slope, n , indicates adsorption effectiveness. Freundlich parameters for Basic Red 46 dye removal (q_m and K) were tabulated at Table 1. It was found that $n_f < 1$ indicated that the dye sorption process onto the prepared PAN nanoparticles was not favorable. Accordingly, dye sorption process onto PAN material obey Langmuir isotherm. As Langmuir isotherm model supposes a monolayer coverage and symmetrical activity division on the materials surfaces. So it can be predicted that the Langmuir model was suitable to analyses the experimental data compared with Freundlich isotherm model.

3.4. Kinetic Models of Dye Adsorption Process

The dye removal rate from the aqueous solution by solid sorbents is essential to evaluate the adsorption kinetics using theoretical models in order to design and control the sorption process units. Therefore, studying the adsorption kinetics of a material is so important, as it gives information about the adsorption mechanism. Moreover, it helps in choosing the appropriate kinetic model (Elkady *et al.*, 2015). Owing to control and design the sorption process units, the pseudo first-order and pseudo-second-order models were applied to

investigate the adsorption of Basic red 46 dye onto the prepared PAN nanoparticles.

The Lagergren first-order equation is given as

$$\ln(q_e - q_t) = \ln q_e k_1 t \quad (5)$$

where q_e and q_t are amounts of dye ions sorbed (mg/g) at equilibrium and at time t (min), respectively. k_1 (min^{-1}) is the first-order reaction rate constant (Figure 13). If the pseudo-first order kinetics is applicable to the experimental data, a plot of $\ln(q_e - q_t)$ versus t should present a linear relationship as shown in Figure 12, which investigated low R^2 value that recorded as 0.5076 for PAN. Also, the estimated values of q_e calculated with the equation, differed from the experimental values, (calculated=0.532 mg/g for PAN, experimental=1.320 mg/g) for PAN, so, the first-order kinetic model was not appropriate to describe the sorption process for the prepared PAN nanoparticles. The kinetic data were further analyzed using the pseudo second-order model expressed as:

$$\frac{t}{q_e} = \frac{1}{k_2 q_e^2} + \left(\frac{t}{q_e}\right) \quad (6)$$

where the equilibrium adsorption capacity (q_e), and the pseudo second-order constants k_2 ($\text{g}/(\text{mg min})$) can be determined experimentally from the slope and intercept of plot t/q_e versus t (Figure 14). The model fits the kinetic data very well as R^2 has very high value ($R^2 = 0.990$). The kinetics of Basic Red 46 sorption onto PAN material could be explained well with a second order equation. Results suggest that the rate-limiting step in these adsorption processes may be chemisorptions involving valent forces. Additionally, comparison of the calculated values of q_e that resulted from the intersection points of the second-degree reaction kinetic curve (14) with those obtained from the experimental data (Table 2) was performed. It was indicated that the true values were approximately equivalent. So, the second-order rate expression fit the experimental data most adequately.

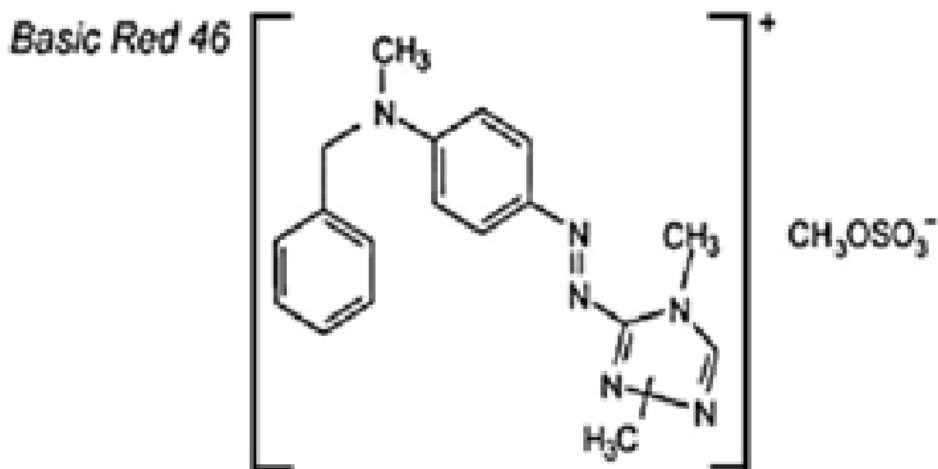


Figure 1: Molecular structure of Basic Red 46 (Sarioglu *et al.*, 2007).

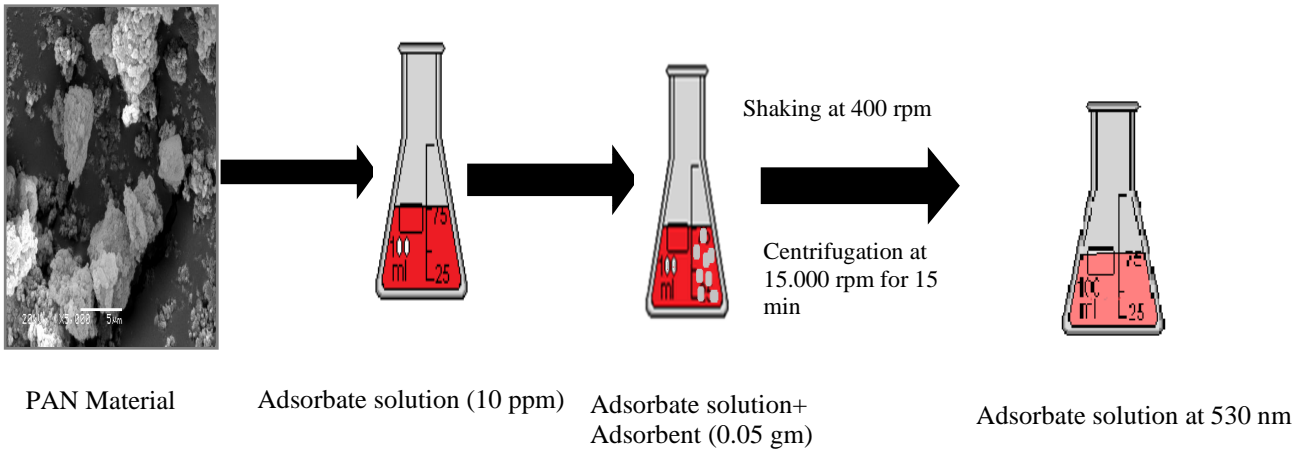


Figure 2: An illustration scheme of dye removal process using PAN Material.

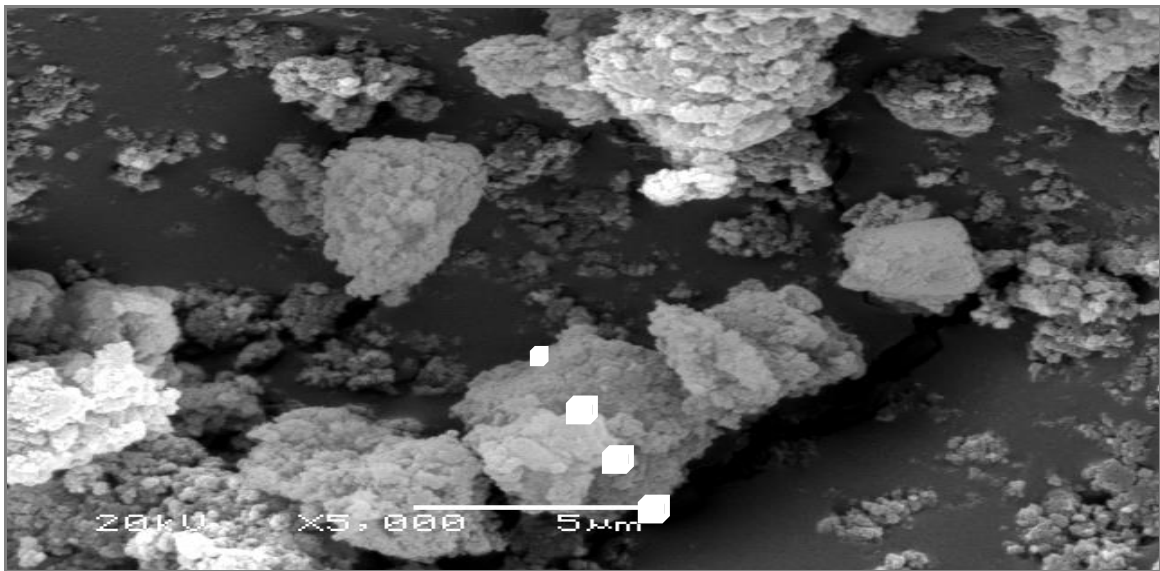


Figure 3: SEM image of the prepared PAN material

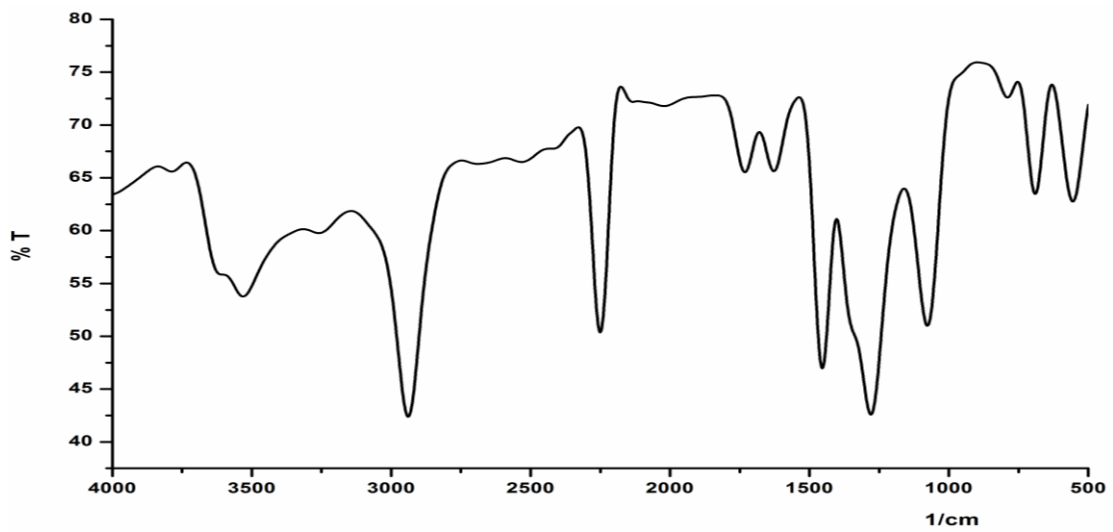


Figure 4: FT-IR spectra of the prepared PAN material.

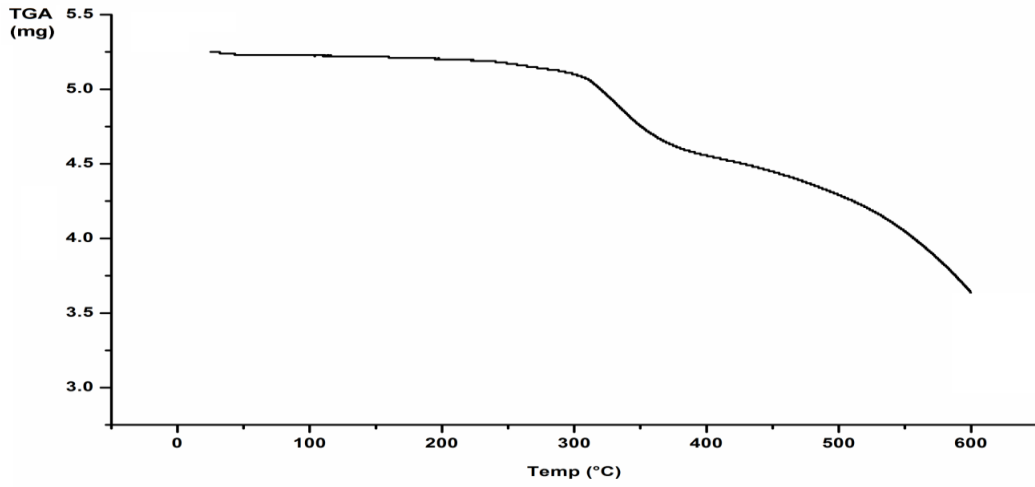


Figure 5: TGA of the prepared PAN material.

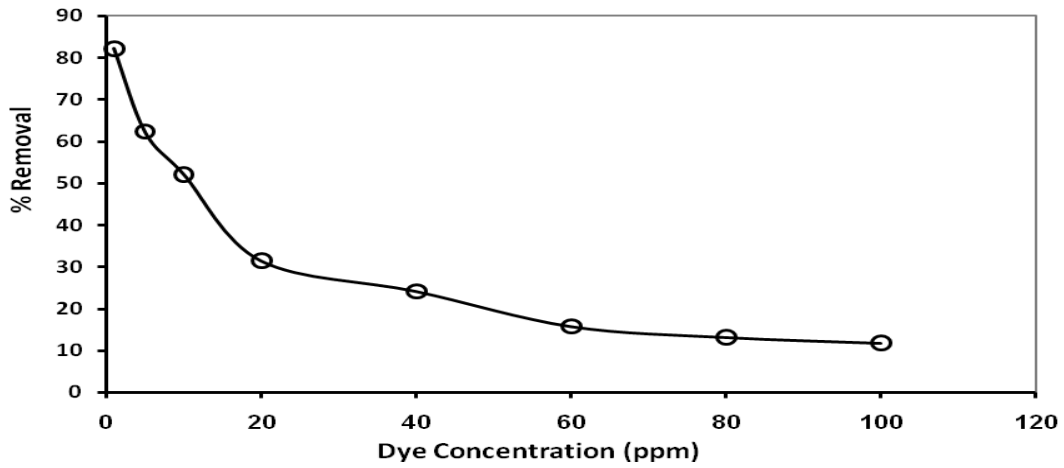


Figure 6: Effect of dye concentration on dye adsorption process onto PAN prepared material (contact time=240 min, material dosage=0.05 g, temperature=25°C and pH=7).

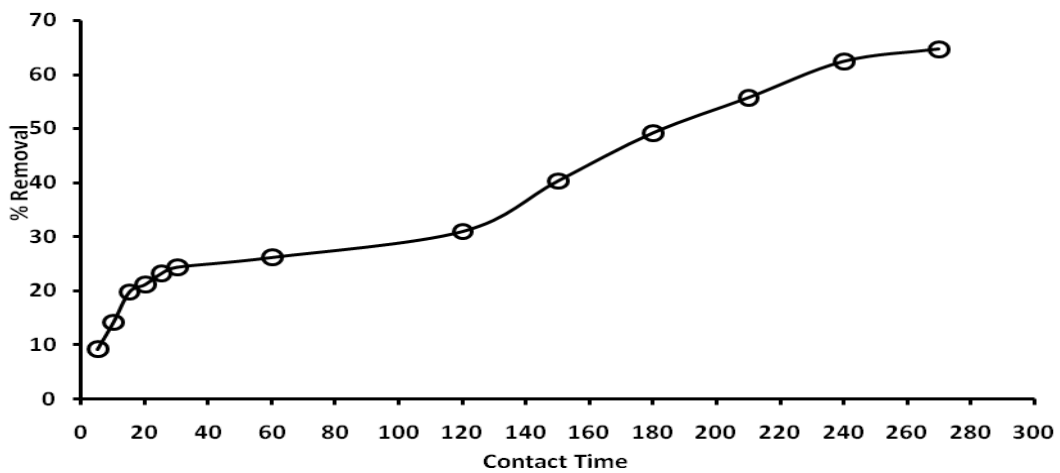


Figure 7: Effect of Contact Time on dye adsorption process onto PAN prepared material (Initial dye concentration= 5 ppm, material dosage=0.05 g and pH=7).

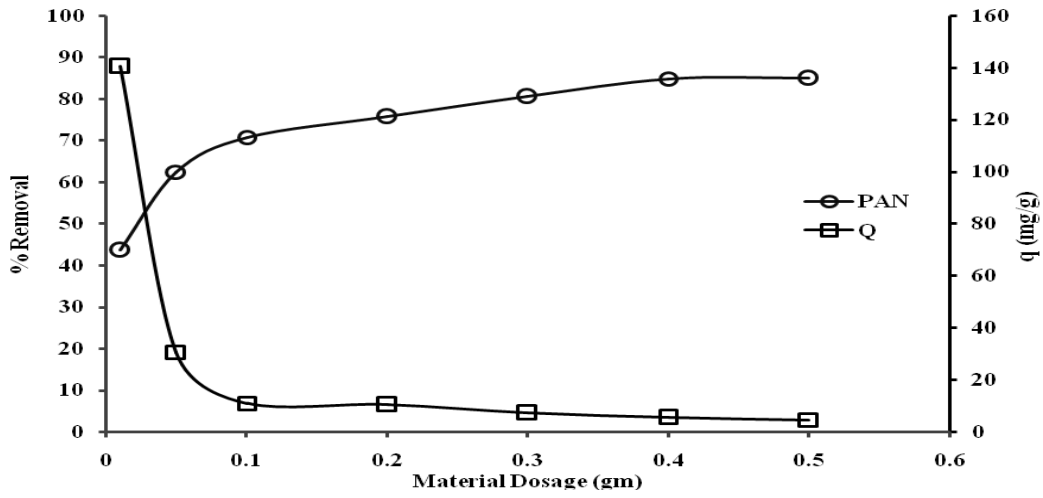


Figure 8: Effect of adsorbent dosage (contact time= 240 min; dye concentration= 5ppm and pH= 7).

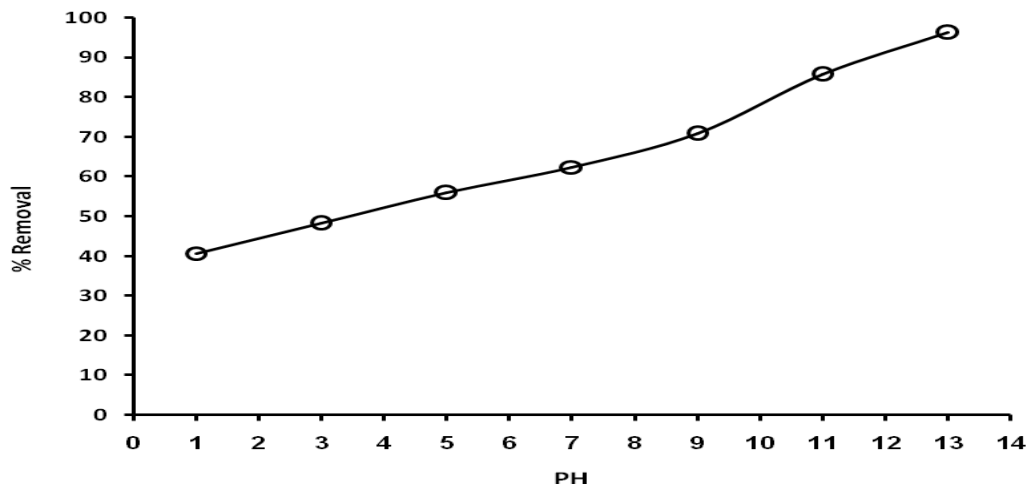


Figure 9: Effect of solution pH on dye adsorption (contact time= 240 min; adsorbant dosage= 0.05 g and dye concentration= 5ppm).

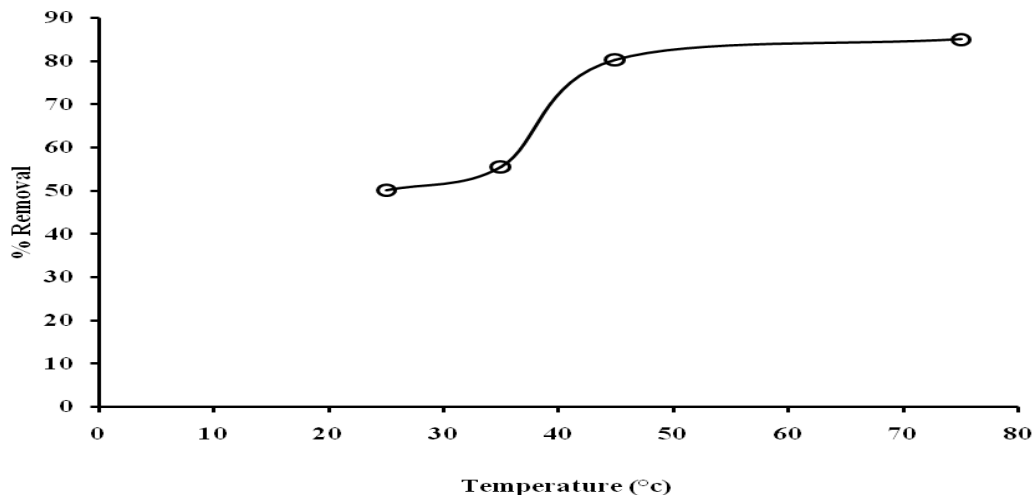


Figure 10: Effect of Temperature on dye adsorption (contact time= 240 min; adsorbant dosage= 0.05 g and dye concentration= 5ppm).

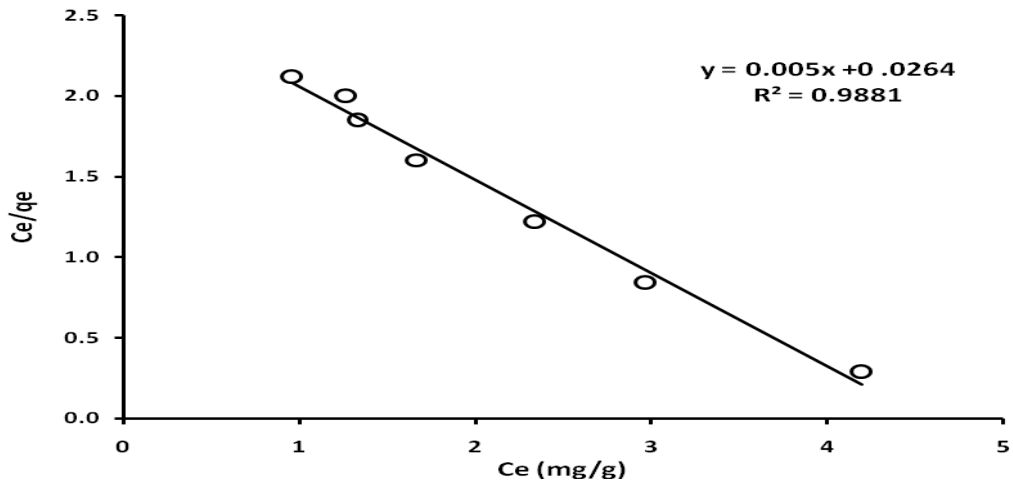


Figure 11: Langmuir Adsorption Isotherm onto PAN Material.

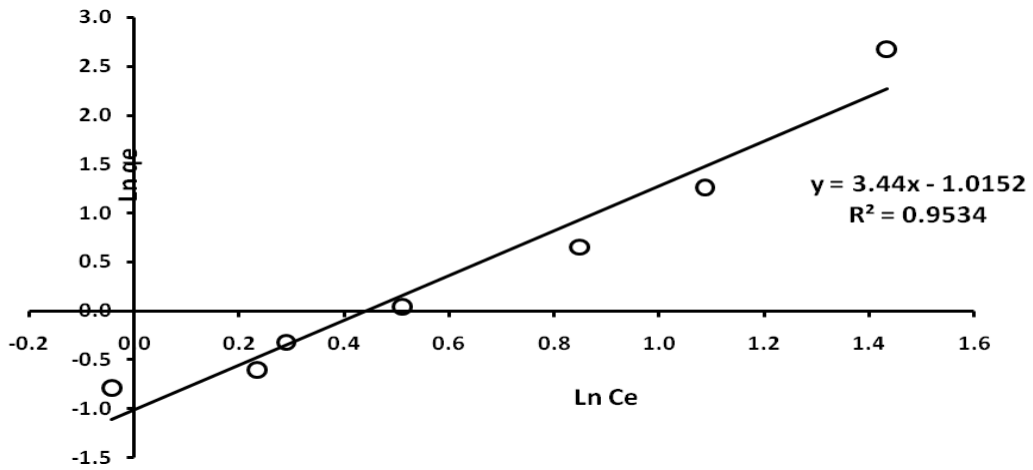


Figure 12: Freundlich Adsorption Isotherm onto PAN Material.

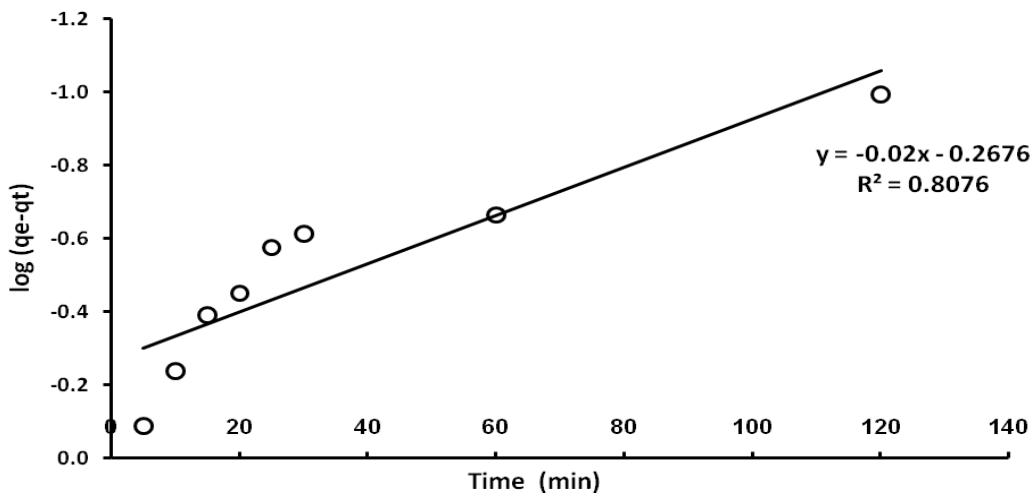


Figure 13: Pseudo-first-order kinetics for adsorption of Basic Red 46 onto PAN Material.

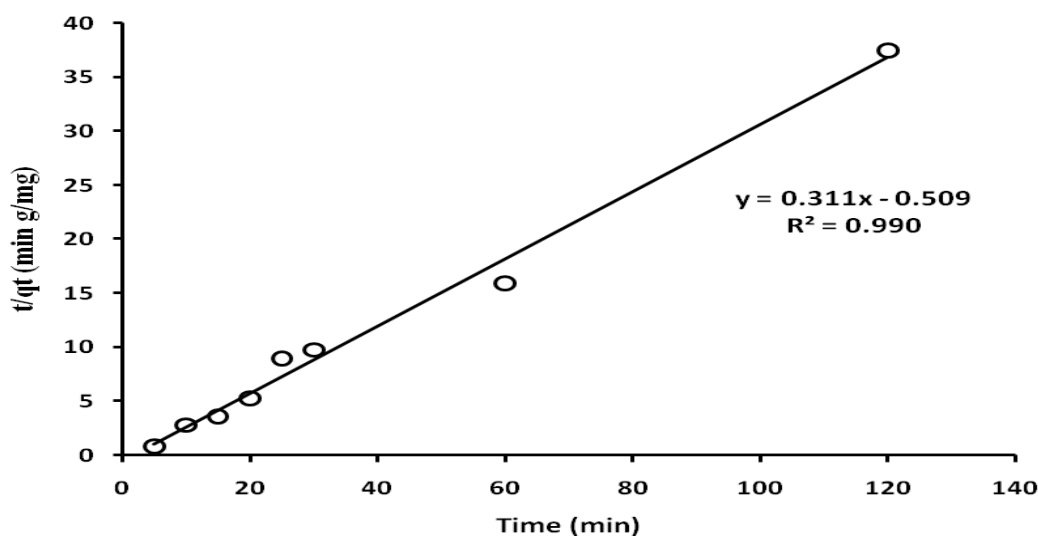


Figure 13: Pseudo-Second-order kinetics for adsorption of Basic Red 46 onto PAN Material.

Table 1: Estimated Equilibrium Parameters for Dye Adsorption onto PAN Material.

Equilibrium isotherm					
Langmuir constant			Freundlich constant		
q _m (mg/g)	K _L (L/mg)	R ²	K _F (mg/g)	n _F	R ²
200	0.189	0.9889	2.759	0.29	0.953

Table 2: Kinetic parameters of dye adsorption onto PAN Material.

Kinetic model		Pseudo-first order			Pseudo-second order			
Dye concentration (mg/L)	(q _e) _{exp} (mg/g)	(q _e) _{cal} (mg/g)	K ₁ (min ⁻¹)	R ²	(q _e) _{exp} (mg/g)	(q _e) _{cal} (mg/g)	K ₂ (g/mg min)	R ²
5	1.320	0.532	0.02	0.8076	3.211	2.936	0.6108	0.990

4. Conclusion

PAN nanoparticles had been prepared through precipitation polymerization technique, its ability as adsorbant material for the removal of acationic dye (Basic Red 46) from a polluted water samples had been studied. The prepared material morphological structure had been investigated through SEM images; also, TGA and FT-IR have also applied. The experimental results proved that the improvement in material dosage from 0.025 to 0.5g enhanced the dye removal percentage as it increased from 43% to 85%. Meanwhile, the increment in initial dye concentrations had negative impact on the dye sorption process, as the removal decreased from 82.8% to 11.8% when the initial dye concentration increased from 1-100 ppm. The equilibrium isotherm models applicability of dye adsorption onto the prepared PAN nanoparticles had been studied and its results prevailed that the dye adsorption occurred onto PAN surface as monolayer coverage. Also, the kinetics of dye adsorption rate was expressed well by the pseudo-second order kinetic equation

which suggested that the main adsorption mechanism was chemisorption process. This study concluded that the prepared PAN nanoparticles could be used as an adsorbate for the removal of different cationic dye pollutants from aquatic environments.

References

- Abu-Saied, M.; Abdel-Halim, E.; Fouda, M.; Al-Deyab, S. (2013). Preparation and Characterization of Iminated Polyacrylonitrile for the Removal of Methylene Blue from Aqueous Solutions. International Journal of Electrochemical Science 8, 5121 – 5135.
- Aksakala, O.; Uzun, H. (2010). Equilibrium, kinetic and thermodynamic studies of the biosorption of textile dye (Reactive Red 195) on to Pinussylvestris. L. Journal of Hazardous Materials, 181, 666–672.
- Al-Qodah, Z. (2000): Adsorption of dyes using shale oil ash. Water Research 34; 17, 4295-4303.

- Alkan, M. and Dogan, M. (2003): Adsorption kinetics of Victoria blue onto perlite, *Fresen. Environ. Bull.* 12, 418–425.
- Araujo, M.M.; Teixeira, J.A. (1997). Trivalent chromium sorption on alginate beads. *International Bio deterioration and Biodegradation*, 40, 63–74.
- Bayramoglu, G. and Arica, M. Y. (2013). Removal of reactive dyes from wastewater by acrylate polymer beads bearing amino groups: isotherm and kinetic studies. *Coloration Technol*, 129, (2), 114-124
- Coats, A.; Redfern, J. (1963). Thermogravimetric analysis. A review. *Analyst*, 906-924.
- Crini, G.; Badot, P.M. (2008). Application of chitosan, a natural amino polysaccharide, for dye removal from aqueous solutions by adsorption processes using batch studies: a review of recent literature, *Progress in Polymer Science*, 33 (4), 399–447.
- Deniz, F. and Karaman, S. (2011). Removal of Basic Red 46 dye from aqueous solution by pine tree leaves. *Chemical Engineering Journal*, 170, 67–74.
- El-Aassar, M. R. (2013). Functionalized electro spun nanofibers from poly (AN-co-MMA) for enzyme immobilization. *Journal of Molecular Catalysis B: Enzymatic*, 85, 141–148.
- EL Alouani, M.; Alehyen, S.; EL Achouri, M.; Taibi, M.; (2018). Removal of Cationic Dye – Methylene Blue from Aqueous Solution by Adsorption on Fly Ash-based Geopolymer. *Journal of Materials and Environmental Sciences*, 9, 1, 32-46.
- El Haddad, M.; Mamouni, R.; Saffaj, N.; Lazar, S. (2012). Removal of a cationic dye -Basic Red 12- from aqueous solution by adsorption onto animal bone meal. *Journal of the Association of Arab Universities for Basic and Applied Sciences*, 12, 48–54.
- Elkady, M.F.; Hussien, M.; Abou-rady, R. (2015). Equilibrium and kinetics behavior of oil spill process onto synthesized nano-activated carbon. *American Journal of Applied Chemistry*, 3, 22-30.
- El-Kady, M.; El-Aassar, M.R.; El Batrawy, O.; Ibrahim, M.; Hassan, H.; Fakhry, H. (2018). Equilibrium and Kinetic Behaviors of Cationic Dye Decolorization Using Poly (AN-co-Py)/ZrO₂ Novel Nanopolymeric Composites. *Advances in Polymer Technology*, 37(3), DOI 10.1002/adv.21716.
- Gorza, F.; Pedro, G.; Da Silva, R.; Medina-Llamas, J.C.; Alcaraz-Espinoz, J.J.; Chávez-Guajardo, A.E.; DeMelo, C.P. (2017). Electrospun polystyrene (emeraldine base) mats as high-performance materials for dye removal from aqueous media. *Journal of the Taiwan Institute of Chemical Engineers*, 82 <https://doi.org/10.1016/j.jtice.2017.10.034>
- Hadi, A. (2013): Dye Removal from Colored Textile Wastewater Using Synthesized Chitosan. *International Journal of Science and Technology* 2; 4.
- Haider, S.; Binagag, F., Haider, A.; Al- Masry, W. (2014). Electrospun oxime-grafted-poly acrylonitrile nanofiber membrane and its application to the adsorption of dyes. *Journal of Polymer Research*, 21:371.
- Hameed, B. and Ahmad, A. (2009). Batch adsorption of methylene blue from aqueous solution by garlic peel, an agricultural waste biomass, *J. Hazar. Mater.* 164, 870–875.
- Han, S.; Liu, K.; Hu, L.; Teng, F.; Yu, P.; Zhu, Y. (2017). Superior Adsorption and Regenerable Dye Adsorbent Based on Flower-Like Molybdenum Disulfide Nanostructure. *Scientific Reports*, 7:43599, DOI: 10.1038/srep43599.
- Hu, L.; Yang, Z.; Wang, Y.; Li, Y.; Fan, D.; Wu, D.; Wei, Q.; Du, B. (2017). Facile preparation of water soluble hyper branched polyamine functionalized multi walled carbon nanotubes for high-efficiency organic dye removal from aqueous solution. *Scientific Reports* 7:3611, DOI:10.1038/s41598-017-03490-6.
- Ibrahim, G.P.; Isloor, A.M.; Inamuddin; Asiri, A.M.; Ismail, N.; Ismail, A.M.; Ashraf, G.M. (2017). Novel, one-step synthesis of zwitterionic polymer nanoparticles via distillation-precipitation polymerization and its application for dye removal membrane. *Scientific Reports*, 7:15889, DOI:10.1038/s41598-017-16131-9.
- Janaki, V.; Vijayaraghavan, K.; Byung-Taek, O.; Ramasamy, A. K.; Kamala-Kannan, S. (2012). Synthesis, characterization and application of cellulose/polyaniline nanocomposite for the treatment of simulated textile effluent. *Cellulose*, 20, 1153–1166.
- Jianlong, W.; Xinmin, Z.; Decai, D.; Ding, Z. (2001). Bioadsorption of Lead (II) from Aqueous Solution by Fungal Biomass of *Aspergillus niger*, *Journal of Biotechnology*, 87 (3), 273-277.
- Kalavathy, M.H. and Miranda, L.R. (2010): Comparison of copper adsorption from aqueous solution using modified and unmodified *Hevea brasiliensis* saw dust. *Desalination* 255, 165–174.
- Kaouah, F.; Boumaza, S.; Berrama, T.; Trari, M.; Bend jama, Z. (2013). Preparation and characterization of activated carbon from wild olive cores (oleaster) by H₃PO₄ for the removal of Basic Red 46. *Journal of Cleaner Production*, 54, 296-306.
- Karim, A.B.; Mounir, B.; Hachkar, M.; Bakasse, M. and Yaacoubi, A. (2009) Removal of Basic Red 46 dye from aqueous solution by adsorption onto Moroccan clay. *Journal of Hazardous Materials*, 168, 304–309.
- Lou, T.; Cui, G.; Xun, J.; Wang, X.; Feng, N.; Zhang, J. (2018). Synthesis of a terpolymer based on chitosan and lignin as an effective flocculant for dye removal., *Colloids and Surfaces A: Physicochemical and Engineering Aspects*, 537, 149- 154, <https://doi.org/10.1016/j.colsurfa.2017.10.012>
- Luo, X.P.; Fu, S.Y.; Du, Y.M.; Guo, J.Z.; Li, B. (2016). Adsorption of methylene blue and malachite green from aqueous solution by sulfonic acid group modified

- MIL-101. Microporous and Mesoporous Materials, 237, doi: 10.1016/j.micromeso.2016.09.032.
- Mahmoodi, N.; Najafi, F.; Khorramfara, S.; Aminia, F. and Aramic, M. (2011): Synthesis, characterization and dye removal ability of high capacity polymeric adsorbent: Polyaminoimide homopolymer. *Journal of Hazardous Materials* 198, 87– 94.
- Mohy Eldin, M.; Elkady, M. F.; Abu-Saied, M.; Abdel Rahman, A.; Soliman, E.; Elzatahry, A.; Youssef, M. (2010). Removal of Cadmium Ions from Synthetic Aqueous Solutions with a Novel Nanosulfonated Poly (glycidylmethacrylate) Cation Exchanger: Kinetic and Equilibrium Studies, *Journal of Applied Polymer Science*, 118, 3111–3122.
- Musale, D.; Kumar, A. (2000). Effects of surface crosslinking on sieving characteristics of chitosan/poly (acrylonitrile) composite nanofiltration membranes. *Separation and Purification Technology*, 21, 27 – 38.
- Prachi, Gautam P.; Madathil, D. and Brijesh, Nair A. (2013): Nanotechnology in Waste Water Treatment: A Review. *International Journal of Chem Tech Research* 5, 2303-2308.
- Salama, A. (2017). New sustainable hybrid material as adsorbent for dye removal from aqueous solutions, *Journal of Colloid and Interface Science*. 487, 348-353, doi: <http://dx.doi.org/10.1016/j.jcis.2016.10.034>
- Sarioglu, M.; Bali, U.; Bisgin, T. (2007). The removal of C.I. Basic Red 46 in a mixed methanogenic anaerobic culture. *Dyes and Pigments*, 74, 223-229.
- Satapanajaru, T.; Chompuchan, C.; Suntornchot, P. and Pengthamkeerati, P. (2011): Enhancing decolorization of Reactive Black 5 and Reactive Red 198 during nano zerovalent iron treatment. *Desalination* 266, 218–230.
- Sharma, K.; Sharma, S.; Sharma, S., Singh, P.; Kumar, S.; Grover, R. and Sharma, p. (2007): A comparative study on characterization of textile wastewaters (untreated and treated) toxicity by chemical and biological tests. *Chemosphere* 69, 48–54.
- Srivastava, V.C.; Swamy, M.M.; Mall, I.D.; Prasad, B. and Mishra, I.M. (2006): Adsorptive removal of phenol by bagasse fly ash and activated carbon: equilibrium, kinetics and thermodynamics. *Colloids and Surfaces A: Physicochemical and Engineering Aspects* 272, 89–104.
- Srivastava, V.C.; Mall, I.D.; and Mishra, I.M. (2008): Removal of cadmium (II) and zinc (II) metal ions from binary aqueous solution by rice husk ash. *Colloids and Surfaces A: Physicochemical and Engineering Aspects* 312, 172– 184.
- Sun, Y.; Li, X.; Cao, J.; Zhang, W. and Wang, H. (2006): Characterization of zero-valent iron nanoparticles. *Advances in Colloid and Interface Science* 120, 47–56.
- Tiwari, D.; Singh, S. and Sharma, N. (2014): Sorption of methylene blue on treated agricultural adsorbents: equilibrium and kinetic studies. *Applied Water Science* 5; 1, 81–88.
- Wua, T.; Cai, X.; Tan, S.; Li, J. and Yang, W. (2011): Adsorption characteristics of acrylonitrile, p-toluenesulfonic acid, 1-naphthalenesulfonic acid and methyl blue on graphene in aqueous solutions. *Chemical Engineering Journal*, 173, 144–149.

الملخص العربي

ازالة الاصباغ من المخلفات السائلة لمصانع الغزل والنسيج باستخدام ماده النانو بولي اكريلونيتريل المحضرة

محمود سالم إبراهيم¹
محمد رمضان الاعصر²

امنيه عبد السلام البطاروى^{1*}
هالة فخري الحسيني¹

¹قسم العلوم البيئية - كلية العلوم - جامعه دمياط - مدينه دمياط الجديده - دمياط - مصر .
²قسم بحوث البوليمرات- معهد بحوث التكنولوجيا المتقدمه والمواد الجديده - الهيئه العامه لمدينه
الأبحاث العلمية والتطبيقات التكنولوجية - الاسكندريه.

يعتبر تلوث المياه من اهم ملوثات البيئه وذلك لان تأثيره السلبي لا يقتصر فقط على الاضرار بصحه الانسان والبيئه بل يمتد الى التأثير على الحياه الاجتماعيه والاقتصاديّه. ويوجد العديد من ملوثات المياه من اهمها بل واكثرها خطوره مياه الصرف الناتجه من صناعات الغزل والنسيج وذلك لانها عباره عن خليط من الاصباغ و الملوثات العضويه والاملاح الكليه الذائبه. تقدم تقنية النانو مواد جديده في مجال معالجة مياه الصرف الصحي وخاصة إزالة الصبغة، حيث تعتبر جزيئات البولي اكريلونيتريل (PAN) النانوية واحده من أكثر المواد الواعده في مجال إزالة الصبغة. تم تحضير جزيئات PAN النانوية باستخدام طريقه بلمره الترسيب في وسط مائي كحولي، وتم توصيفها توصيفا كاملا باستخدام الميكروسكوب الالكتروني SEM , التحليل الحراري TGA, والتحليل باستخدام FT-IR. في هذه الدراسه تم استخدام صبغه (BR 46) وهي صبغه موجب الشحنة وتم استخدامها كنموذج ملوث للمياه وذلك لكثرة استخدامها في صناعه الغزل والنسيج، كما تم دراسه العوامل المؤثره على ازاله الصبغه باستخدام جزيئات البولي اكريلونيتريل من خلال تجارب batch mode experiments. ولقد اوضحت النتائج المعملية ان اقصى نسبة ازاله للصبغه كانت حوالي 62.4% بعد مرور حوالي 240 دقيقه من بدايه التفاعل بين ماده المحضره والصبغه باستخدام 0.05جم من ماده المحضره وتركيز 5 مجم/لتر من الصبغه. ايضا تم تطبيق نماذج التوازن equilibrium isotherm . ومن خلال النتائج السابقه يتضح مدى فاعليه ماده المحضره PAN في ازاله الاصباغ الناتجه من صناعه الغزل والنسيج.



Journal of Environmental Sciences

JOESE 5



Decolorization of Textile Wastewater Using Fabricated Poly Acrylonitrile (PAN) Nanoparticles

Omnya A. El-Batrawy^{1*}, Mahmoud S. Ibrahim¹, Hala Fakhry^{1,2} and M. R. El-Aassar²

¹*Environmental Sciences Department, Faculty of Science, Damietta University, New Damietta City, Damietta, 34517, Egypt.*

²*Polymer Materials Research Department, Advanced Technology and New Materials Researches Institute, City of Scientific Researches and Technological Applications, New Borg El-Arab City, Alexandria, 21934 Egypt.*

Reprint

Volume 47, Number 3-4 : 75 -87

(2018)